

ULTIMET[®] alloy


A cobalt-base alloy with exceptional resistance to galling, cavitation erosion, slurry erosion, liquid droplet impact, and various forms of corrosive attack.

ULTIMET alloy exhibits superior weldability and may be used to weld overlay critical surfaces to improve their resistance to corrosion-wear. The alloy is available in a variety of wrought forms, as well as castings and powders.


Contents

Applications	2
Principal Features	3
Erosion	4
Galling	5
Abrasion Wear	6
Localized Corrosion	7
Aqueous Corrosion	8
Isocorrosion Curves	9
Physical Properties	10
Hardness	11
Tensile Data	12
High Temperature Corrosion	14
Welding	15
Health and Safety	16
Weld Overlay	17
Machining	18
Availability	19
Sales Office Addresses	20

TYPICAL APPLICATIONS

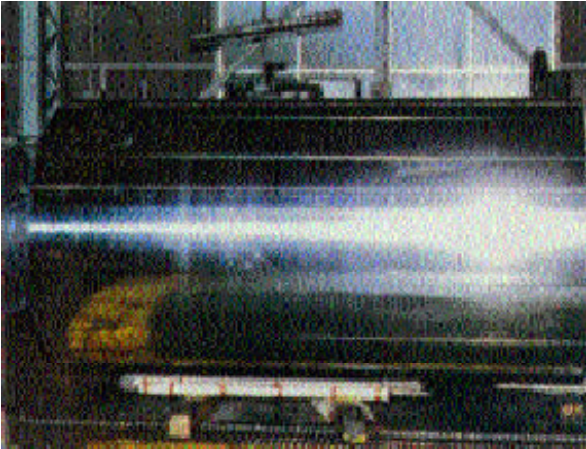

ULTIMET alloy electrogalvanizing rolls have been used successfully in the production of galvanized steel for automobiles in the Far East and Europe. The corrosion/wear rate of ULTIMET alloy in this application is about half that of the previously used Ni-Cr-Mo alloy.

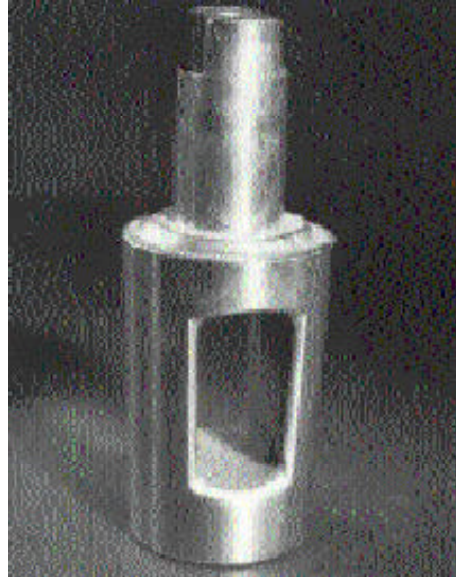

The use of an ULTIMET weld overlay on the plug of a valve solved a problem of failure by erosion at a large chemical company in the U.S. The valve protected with ULTIMET has so far lasted three times as long as the unprotected valve, and is still in service.



ULTIMET cast nozzles are now standard for a major incinerator scrubber manufacturer in Europe. In this application, ULTIMET alloy has out-performed ceramics and cast Co-Cr-W and Ni-Cr-Mo alloys.



ULTIMET is the standard shielding material for fans used by a large fiberglass company in North America. It has proved resistant to erosion/corrosion in fiberglass manufacturing, and is preferred over the Co-Cr-W alloys because of its relatively high ductility.

PRINCIPAL FEATURES

Outstanding Corrosion-Wear Resistance

ULTIMET[®] alloy is a cobalt-chromium alloy which offers excellent corrosion resistance comparable to that of the HASTELLOY[®] alloys. ULTIMET alloy exhibits outstanding wear resistance similar to that of the STELLITE[®] alloys. Also, ULTIMET alloy possesses high tensile strength comparable to many duplex stainless steels combined with excellent impact toughness and ductility.

ULTIMET alloy is an ideal welding material with exceptional ductility and resistance to weld cracking. It is very easy to apply as an overlay, compared with the traditional cobalt-base wear alloys. With ULTIMET alloy, cracking of the overlay is not a consideration, and multiple layers may be applied, with little or no preheat.

Product Forms

ULTIMET alloy is available in most common wrought product forms: plate, sheet, billet, bar, wire, and covered electrodes.

Wrought forms of this alloy are furnished in the solution heat-treated condition, unless otherwise specified.

Licenseses of Haynes International produce ULTIMET alloy remelt bar for castings and ULTIMET gas-atomized powders for plasma transferred arc, plasma spray, and high-velocity oxy-fuel processes.

Applications

Some of the areas of use for ULTIMET alloy are:

- Agitators
- Blenders
- Bolts
- Dies
- Extruders
- Fan Blades
- Filters
- Glass Plungers
- Nozzles
- Pumps
- Rolls
- Screw Conveyors
- Valve Parts

Field Test Program

Samples of ULTIMET alloy are readily available for laboratory or in-plant corrosion testing. An analysis of the tested material can be performed and the results provided to the customer as a technical service. Contact any of the locations shown on the back cover of this brochure for test coupons and information.

Specifications

ULTIMET alloy is covered by ASME Section VIII, Division 1, Code Case 2121. Plate, sheet, strip, and bar are covered by ASTM Specification B-815 and B-818. DIN specification is CoCr26Ni9Mo5W No. 2.4681 (all forms). The UNS number for ULTIMET alloy is R31233. ULTIMET alloy is covered by Section 4.1.6.3 of NACE Standard MR-01-75.

Material Safety Data Sheets

For information concerning material safety data, ask for Material Safety Data Sheet H1072.

Nominal Chemical Composition, Weight Percent


Co ^a	Cr	Ni	Mo	Fe	W	Mn	Si	N	C
54	26	9	5	3	2	0.8	0.3	0.08	0.06

^a As balance

COMPARATIVE RESISTANCE TO EROSION


Alloy	Erosion Depth/Rate		
	Cavitation (mm)	Slurry (microns)	Solid Particle (mm ³ /g x 10 ⁴)
ULTIMET [®] alloy	0.0068	0.740	10.34
HAYNES [®] 6B alloy	0.0073	0.460	10.44
HAYNES 625 alloy	0.0800	1.660	13.33
HASTELLOY [®] C-276 alloy	0.1128	1.420	12.65
Carpenter 20CB-3 [®] alloy	0.2743	1.980	11.06
Type 316L Stainless Steel	0.1802	1.310	12.38
FERRALIUM [®] alloy 255	0.1336	-	-

Cavitation Test

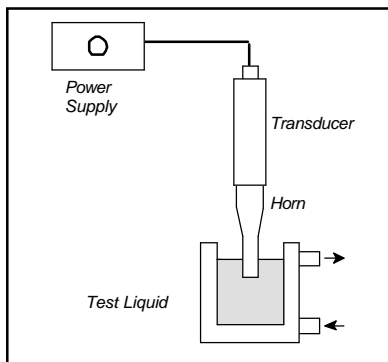


ASTM Standard G 32
 Frequency-20 kHz
 Amplitude-0.05 mm
 Liquid-Distilled Water
 Test Duration-24 hr.
 Room Temperature

Slurry Test

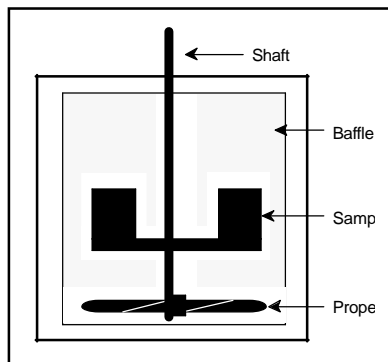


Medium-80 microns Alumina
 in Tap Water
 Velocity-5 m/s
 Impact Angle-30°
 Particle Loading-0.12 kg/l
 Test Duration-40 hr.
 Room Temperature

Solid Particle Test

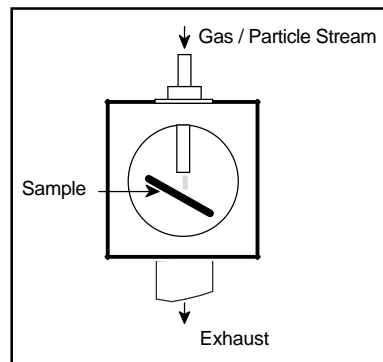

ASTM Standard G 76 (Modified)
 Erodent-400 microns Angular
 Silicon Carbide
 Velocity-20 m/s
 Impact Angle-60°
 Total Flow-80 g of Erodent
 Room Temperature

COMPARATIVE RESISTANCE TO GALLING

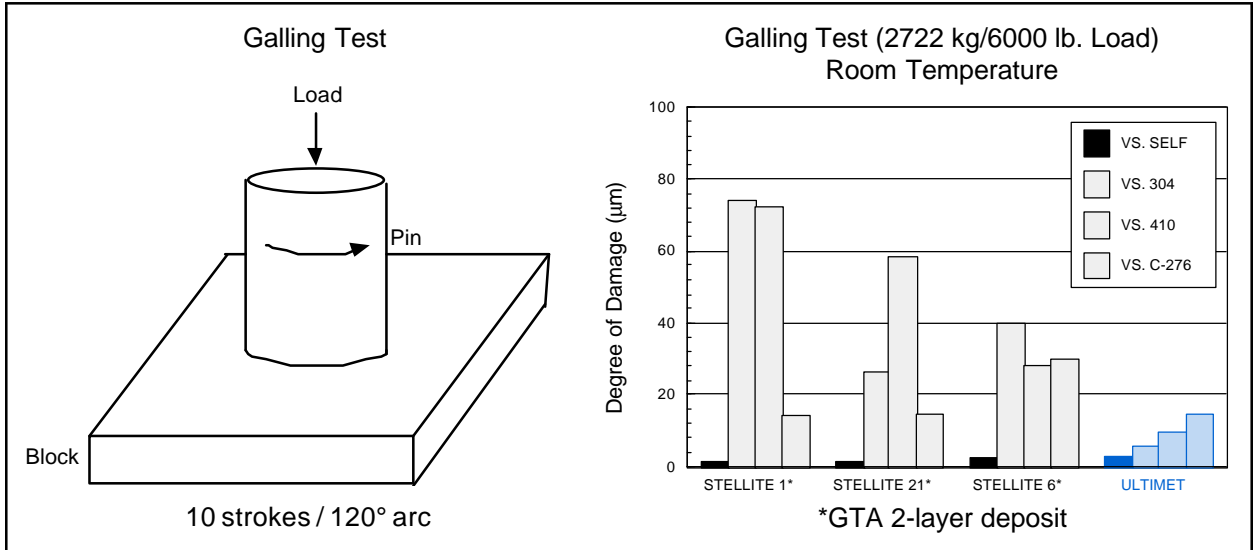


Pin	Block	Degree of Damage, microns Load		
		1361 kg (3000 lb)	2722 kg (6000 lb)	4082 kg (9000 lb)
ULTIMET® alloy	ULTIMET alloy	2.9	2.7	2.0
ULTIMET alloy	1045 Carbon Steel (HRC 32)	7.4	6.6	8.2
ULTIMET alloy	4140 Alloy Steel (HRC 46)	2.3	2.7	2.5
ULTIMET alloy	H-13 Tool Steel (HRC 48)	2.1	2.1	2.0
ULTIMET alloy	Type 304 Stainless Steel	2.5	5.5	18.3
ULTIMET alloy	Type 316L Stainless Steel	1.4	1.2	0.7
Type 316L Stainless Steel	Type 316L Stainless Steel	>100.0	-	-
ULTIMET alloy	Type 410 Stainless Steel	9.4	9.4	17.7
ULTIMET alloy	17-4-PH® Stainless Steel (HRC 39)	3.5	3.5	5.7
17-4-PH Stainless (HRC 39)	17-4-PH Stainless (HRC 39)	57.8	>100.0	>100.0
ULTIMET alloy	HASTELLOY® C-276 alloy	11.4	14.6	17.6
ULTIMET alloy	HAYNES® 718 alloy (HRC 47)	7.1	8.5	11.7
HAYNES 718 alloy (HRC 47)	HAYNES 718 alloy (HRC 47)	18.1	24.0	16.7
ULTIMET alloy	STELLITE® 6**	0.1	0.1	0.1
ULTIMET alloy	STELLITE 6H**	0.1	0.1	0.1
HAYNES 6B alloy	HAYNES 6B alloy	0.6	0.7	0.5
NITRONIC® 60 alloy	NITRONIC 60 alloy	2.5	120.0	111.3

All Wrought Products except:
 ** All-Weld-Metal, GTA weld type


COMPARATIVE RESISTANCE TO ABRASION

Low Stress Abrasion Test

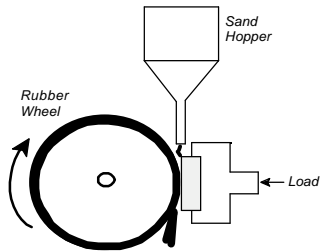

Load: 13.6 kg
 Flow Rate: 390 g/min
 Wheel Speed: 200 rev/min
 Test Revolutions: 2000

High Stress Abrasion Test

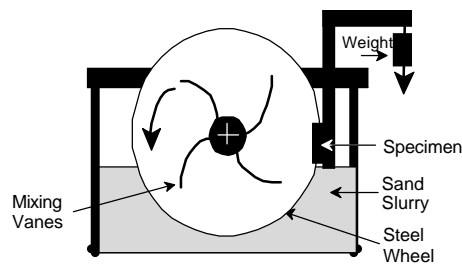


Load: 22.7 kg
 Slurry: 1500g sand/940g water
 Wheel Speed: 240 rev/min
 Test Revolutions: 250

Alloy	Volume Loss, cu mm	
	Low Stress*	High Stress**
ULTIMET® alloy	90.4	56.1
HAYNES® 6B alloy	15.3	57.0
HAYNES 625 alloy	119.3	63.4
HASTELLOY® C-22® alloy	114.0	64.9
HASTELLOY C-276 alloy	123.5	49.8
FERRALIUM alloy 255	97.5	75.0
Type 316L Stainless Steel	140.4	64.8
Type D-2 Tool Steel (HRC 60)	15.2	56.9
Carpenter 20CB-3 alloy	127.9	56.4
NITRONIC 60	145.8	-
Type 1020 Carbon Steel	130.0	-
STELLITE 1***	29.4	-
STELLITE 6***	63.8	-
STELLITE 21***	80.3	-

* ASTM G-65
 ** ASTM B-611
 *** GTAW, 2-layer

Abrasion Data*

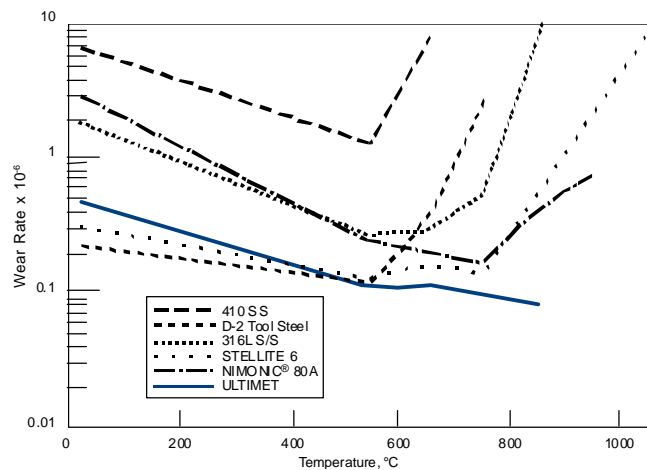

*Reference: Wear, Volume 162-164 (1993), page 441-449

LOCALIZED CORROSION RESISTANCE

Comparative Critical Pitting Temperatures in Oxidizing H₂SO₄-HCl Solution

The chemical composition of the solution used in this test is as follows: 11.5 percent H₂SO₄ + 1.2 percent HCl + 1 percent FeCl₃ + 1 percent CuCl₂. This test environment is a severely

oxidizing acid solution which is used to evaluate the resistance of alloys to localized corrosion. Experiments were performed in increments of solution temperature of 5°C for a 24-hour

exposure period to determine the lowest temperature at which pitting corrosion initiated (observed by examination at a magnification of 40X).

Alloy	Critical Pitting Temperature	
	°C	°F
HASTELLOY® C-22® alloy	120	248
ULTIMET® alloy	120	248
HASTELLOY C-276 alloy	110	230
HAYNES® 625 alloy	75	167
HAYNES 6B alloy	45	113
TYPE 316L Stainless Steel	25	77

Comparative Immersion Critical Crevice Corrosion Temperatures in Oxidizing 6% FeCl₃ Solution for 72 Hours

Alloy	Critical Crevice Corrosion Temperature	
	°C	°F
HASTELLOY C-22 alloy	70	158
ULTIMET alloy	65	149
HASTELLOY C-276 alloy	65	149
HAYNES 625 alloy	30	86
HAYNES 6B alloy	25	77
TYPE 316L Stainless Steel	<0	<32

Comparative Stress-Corrosion Cracking Data

Alloy	45% MgCl ₂ 154°C (309°F)	0.8% NaCl+ 0.2% H ₃ PO ₄ 141°C (286°F)
HASTELLOY C-22 alloy	No Cracks	No Cracks
ULTIMET alloy	Cracked	No Cracks
FERRALIUM® alloy 255	Cracked	No Cracks
Carpenter 20CB-3 alloy	Cracked	No Cracks
Type 316L Stainless Steel	Cracked	Cracked
HAYNES 6B alloy	Broke on Bending	Broke on Bending

AQUEOUS CORROSION DATA

Comparative Aqueous Corrosion Data on Wrought Products

	Concentration, % by weight	Test Temperature		Average Corrosion Rate per Year, mils*			
		°F	°C	ULTIMET® alloy	6B alloy	C-276 alloy	alloy 20CB-3
Hydrochloric Acid	1	Boiling		0.3	170	13	81
Nitric Acid	65	Boiling		6	5434	848	8
P ₂ O ₅ (Commercial Grade)	54	240	116	8	15	28	36
Sulfuric Acid	10	Boiling		99	232	18	22
Sulfuric Acid + 1.2% HCl + 1% FeCl ₃ + 1% CuCl ₂ (ASTM G28B)	23	Boiling		2	2888	55	2720
Sulfuric Acid + 42 g/l Fe ₂ (SO ₄) ₃ (ASTM G28A)	50	Boiling		8	14	250	10

* To convert mils per year (mpy) to mm per year, divide by 40.

Comparative Aqueous Corrosion Data on Cast Product

	Concentration, % by weight	Test Temperature		Average Corrosion Rate per Year, mils			
		°F	°C	ULTIMET alloy ¹	CX-2MW ² (C-22)	AMS 5373 alloy 6 ¹	CF-3M ² (316LSS)
Ferric Chloride	10	Boiling		1	156	19989	20925
Nitric Acid	65	Boiling		8	117	2890	14
P ₂ O ₅ (Commercial Grade)	54	240	116	8	13	35	28
Sulfuric Acid	10	Boiling		84	26	7269	634
Sulfuric Acid + 1.2 HCl + 1% FeCl ₃ + 1% CuCl ₂ (ASTM G28B)	23	Boiling		41	27	3181	3557
Sulfuric Acid + 42 g/l Fe ₂ (SO ₄) ₃ (ASTM G28A)	50	Boiling		10	71	61	27

¹As-Cast Condition ²Cast + Annealed Condition


ISOCORROSION DIAGRAMS*

The isocorrosion diagrams shown on this page were plotted using data obtained in


laboratory tests in reagent grade acids. These data should be used only as a

guide. It is recommended that samples be tested under actual plant conditions.


Resistance to Hydrochloric Acid

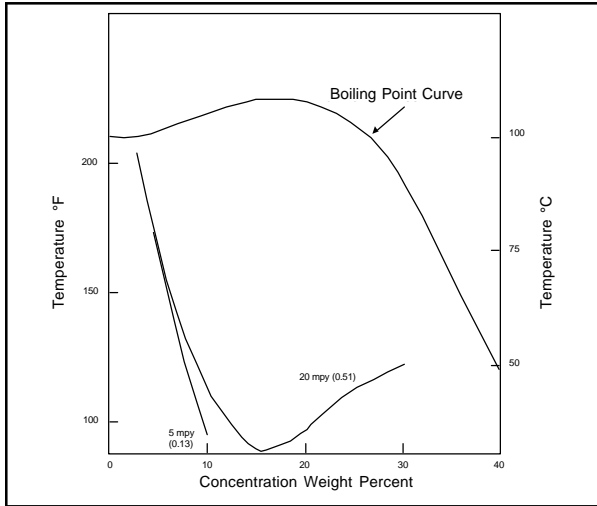


Resistance to Nitric Acid

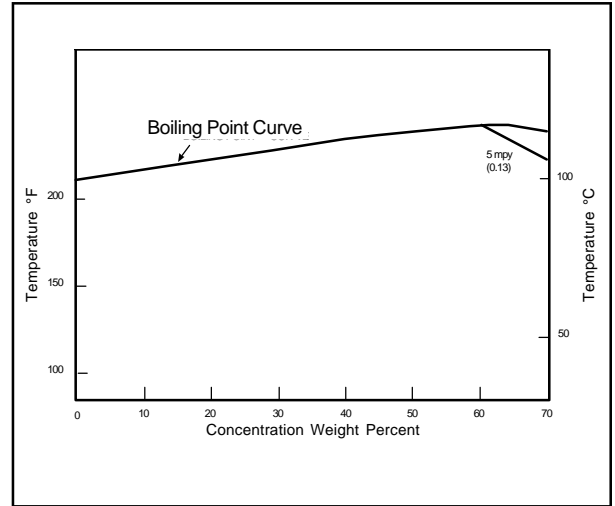

Resistance to Sulfuric Acid

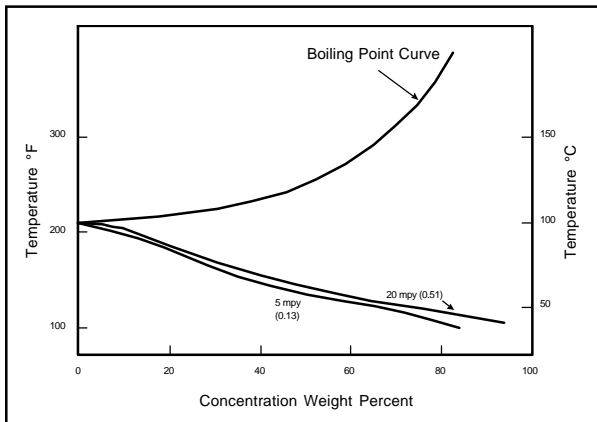

Resistance to Phosphoric Acid

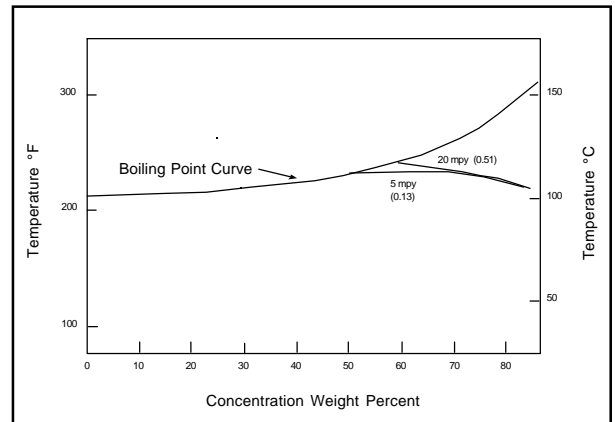

Corrosion rates in parentheses are in mm/year.

* All test specimens were heat-treated at 2050°F (1121°C), water quenched and in the unwelded condition.

TYPICAL PHYSICAL PROPERTIES

Physical Property	Temp., °F	British Units	Temp., °C	Metric Units
Density	75	0.306 lb/in. ³	24	8.47 g/cm. ³
Melting Temperature	2430-2470		1332-1354	
Electrical Resistivity	75	34.2 microhm-in.	23	0.87 microhm-m
	212	35.4 microhm-in.	100	0.89 microhm-m
	392	36.6 microhm-in.	200	0.93 microhm-m
	572	38.1 microhm-in.	300	0.96 microhm-m
	752	39.3 microhm-in.	400	1.00 microhm-m
	932	40.5 microhm-in.	500	1.03 microhm-m
	1112	41.3 microhm-in.	600	1.05 microhm-m
Mean Coefficient of Thermal Expansion	78-200	7.2 microinches/in.-°F	26-93	13.0 x 10 ⁻⁶ m/m-K
	78-400	7.5 microinches/in.-°F	26-204	13.5 x 10 ⁻⁶ m/m-K
	78-600	7.8 microinches/in.-°F	26-316	14.0 x 10 ⁻⁶ m/m-K
	78-800	8.0 microinches/in.-°F	26-427	14.5 x 10 ⁻⁶ m/m-K
	78-1000	8.2 microinches/in.-°F	26-538	14.8 x 10 ⁻⁶ m/m-K
	78-1200	8.4 microinches/in.-°F	26-649	15.1 x 10 ⁻⁶ m/m-K
	78-1400	8.8 microinches/in.-°F	26-760	15.9 x 10 ⁻⁶ m/m-K
	78-1600	9.1 microinches/in.-°F	26-871	16.4 x 10 ⁻⁶ m/m-K
	78-1800	9.4 microinches/in.-°F	26-982	16.9 x 10 ⁻⁶ m/m-K
Thermal Diffusivity	73	0.005 in. ² /sec.	23	3.3 x 10 ⁻⁶ m ² /s
	212	0.005 in. ² /sec.	100	3.5 x 10 ⁻⁶ m ² /s
	392	0.006 in. ² /sec.	200	3.8 x 10 ⁻⁶ m ² /s
	572	0.006 in. ² /sec.	300	4.2 x 10 ⁻⁶ m ² /s
	752	0.007 in. ² /sec.	400	4.5 x 10 ⁻⁶ m ² /s
	932	0.007 in. ² /sec.	500	4.7 x 10 ⁻⁶ m ² /s
	1112	0.007 in. ² /sec.	600	5.0 x 10 ⁻⁶ m ² /s
Thermal Conductivity	73	85 Btu-in./ft. ² hr.-°F	23	12.3 W/m-K
	212	96 Btu-in./ft. ² hr.-°F	100	13.8 W/m-K
	392	108 Btu-in./ft. ² hr.-°F	200	15.6 W/m-K
	572	121 Btu-in./ft. ² hr.-°F	300	17.5 W/m-K
	752	134 Btu-in./ft. ² hr.-°F	400	19.4 W/m-K
	932	149 Btu-in./ft. ² hr.-°F	500	21.5 W/m-K
	1112	166 Btu-in./ft. ² hr.-°F	600	23.9 W/m-K
Specific Heat	73	0.109 Btu/lb.-°F	23	456 J/kg-K
	212	0.112 Btu/lb.-°F	100	470 J/kg-K
	392	0.115 Btu/lb.-°F	200	482 J/kg-K
	572	0.121 Btu/lb.-°F	300	504 J/kg-K
	752	0.126 Btu/lb.-°F	400	525 J/kg-K
	932	0.130 Btu/lb.-°F	500	545 J/kg-K
	1112	0.137 Btu/lb.-°F	600	573 J/kg-K

Typical Dynamic Modulus of Elasticity

Form	Condition	Test Temperature		Average Dynamic Modulus of Elasticity	
		°F	°C	10 ⁶ psi	GPa
Plate	Heat-treated at 2050°F Water Quenched	400	204	31.2	215
		600	316	29.9	206
		800	427	28.6	197
		1000	538	27.4	189
		1200	649	26.1	180

HARDNESS

Average Room Temperature Hardness

Condition	Form	Hardness, Rockwell
Mill Annealed	Sheet	Rc 30
10% Cold Worked	Sheet	Rc 40
20% Cold Worked	Sheet	Rc 43
40% Cold Worked	Sheet	Rc 49
As-Cast	Investment	Rb 96

Comparative Elevated Temperature Hardness

Temperature		Diamond Pyramid Hardness, HV		
		ULTIMET [®] alloy	HAYNES 6B alloy	HAYNES 25 alloy
°F	°C			
Room		296	374	285
800	427	173	269	171
1000	538	162	247	160
1200	649	158	225	150
1400	760	134	153	134
1600	871	89	91	93
1800	982	50	55	52

TENSILE DATA

Typical Tensile Data, Solution Heat-Treated

Form	Test Temperature		Ultimate Tensile Strength, ksi*	Yield Strength at 0.2% Offset, ksi*	Elongation in 2 in. (50.8 mm), %	
	°F	°C				
Sheet	Room		138	72	42	
0.063 in. (1.6 mm)	200	93	135	58	50	
	400	204	134	45	62	
	600	316	130	43	75	
	800	427	120	41	76	
Plate	Room		148	79	36	
1/4 - 1 1/2 in. (6.3 - 38.1 mm)	200	93	143	70	40	
	400	204	143	55	61	
	600	316	138	48	70	
	800	427	133	45	70	
	1000	538	125	38	70	
	1200	649	99	37	66	
	1400	760	76	39	70	
	1600	871	51	28	77	
Bar	Room		147	76	38	
	1/2 - 2 in. (12.7 - 50.8 mm)	200	93	140	70	49
		400	204	140	52	66
		600	316	132	44	77
		800	427	131	43	84
		1000	538	115	40	79

* ksi can be converted to MPa (megapascals) by multiplying by 6.895.

Typical Room Temperature Tensile Data, Aged Material

Condition	Ultimate Tensile Strength, ksi*	Yield Strength at 0.2% Offset, ksi*	Elongation in 2 in. (50.8 mm), %
Mill Annealed	148	79	36
Aged 1000 Hrs 400°F 204°C	148	79	34
Aged 1000 Hrs 600°F 316°C	155	80	47
Aged 1000 Hrs 800°F 427°C	155	81	47
Aged 1000 Hrs 1000°F 538°C	149	77	44
Aged 1000 Hrs 1200°F 649°C	146	85	29
Aged 1000 Hrs 1400°F 760°C	138	77	14
Aged 1000 Hrs 1600°F 871°C	139	71	28
Aged 1000 Hrs 1800°F 982°C	145	71	41

Typical Impact Strength, Plate

Aging Temperature °F °C		Aging Time hours	V-Notch Impact Strength			
			Room Temperature ft.-lb.	Room Temperature Joules	-320°F ft.-lb.	-196°C Joules
Mill Annealed		-	130	176	68	92
400	204	100	141	191		
		1000	150	203		
600	316	100	150	203		
		1000	160	217		
1000	538	100	160	217		
		1000	152	206		
1200	649	100	117	159		
		1000	19	26		
1400	761	100	19	26		
		1000	7	9		
1600	871	100	23	31		
		1000	17	23		
1800	982	100	56	76		
		1000	44	60		

Comparative Impact Strength

Alloy	V-Notch Impact Strength	
	Room Temperature ft.-lb.	Room Temperature Joules
ULTIMET® alloy	130	176
HAYNES® 6B alloy	6	8
Type 316 Stainless Steel	80	108


HIGH TEMPERATURE CORROSION

Comparative Oxidation Data

Static Oxidation Tests 1008 Hours

Alloy	1800°F 982°C		2000°F 1093°C	
	Metal Loss (mm)	Avg. Metal Affected (mm)	Metal Loss (mm)	Avg. Metal Affected (mm)
625	0.01	0.02	0.08	0.12
6B	0.01	0.03	0.35	0.39
ULTIMET®	0.01	0.05	0.40	0.47
800HT®	<0.01	0.09	0.16	0.31
HR-160®	0.02	0.15	0.04	0.26

Resistance to Molten Zinc

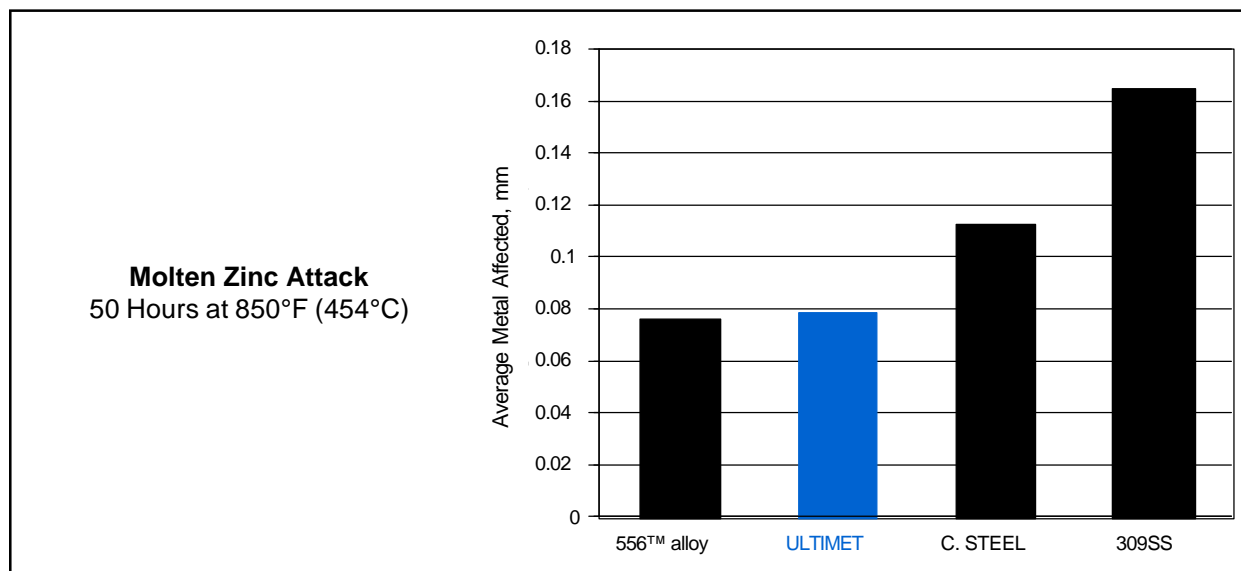

Comparative Resistance to Sulfidation Attack

Environment: Argon-5% Hydrogen-5% Carbon Monoxide-1%
Carbon Dioxide-0.15% Hydrogen Sulfide

Alloy	Metal Loss (mm)	Internal Attack	
		Average (mm)	Maximum (mm)
6B	<0.01	0.06	0.06
ULTIMET® alloy	<0.01	0.06	0.08
HAYNES® HR-160® alloy	<0.01	0.09	0.11
HAYNES 556™ alloy	0.11	0.29	0.36
alloy 800H	0.19	0.41	0.50
alloy 625	Partially Consumed		

Time: 215 Hours
Temperature: 1600°F 871°C

WELDING

ULTIMET alloy is readily welded by gas tungsten arc (GTAW), gas metal arc (GMAW), shielded metal arc (SMAW) and submerged arc (SAW) welding techniques. ULTIMET alloy possesses excellent resistance to hot cracking. The oxyacetylene welding process is not recommended. Post-weld annealing is not necessary with ULTIMET alloy.


Base Metal Preparation

The joint surface and adjacent area should be thoroughly cleaned before welding. All grease, oil, crayon marks, sulfur compounds and other foreign matter should be removed.

Preheating is not required, and weld interpass temperatures should be kept below 93°C (200°F) when possible.

Filler Metal Selection

Matching composition filler metal is recommended for joining ULTIMET alloy. For gas tungsten arc, gas metal arc welding, and submerged arc ULTIMET filler wire is recommended. For shielded metal arc welding, ULTIMET covered electrodes are recommended. Detailed information for ULTIMET alloy is available in Haynes publications H-2089 and H-2099.

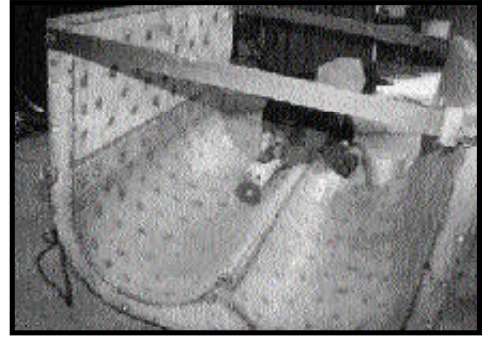

ULTIMET alloy was selected for this green pigment mixer bowl and blade to provide enhanced corrosion and wear resistance. The mixer bowl has been lined with ULTIMET sheet and the blade was weld overlaid with ULTIMET wire.

Typical Transverse Tensile Data, Weldments

Form	Weld Type	Test Temperature		Ultimate Tensile Strength, ksi*	Yield Strength at 0.2% Offset, ksi*	Elongation in 2 in. (50.8 mm), %
		°F	°C			
Plate 1/2 in. (12.7 mm) thick	GTAW	Room		127	89	11
		GMAW (Short)	Room		121	98
	500		260	121	65	19
	1000		538	114	53	28
	GMAW (Spray)		Room		133	93
		500	260	121	67	19
		1000	538	113	65	30
	SMAW	Room		135	97	9
Plate 3/4 in. (19.1 mm) thick	GMAW (Short)	Room		123	86	10
		500	260	116	62	20
		1000	538	98	45	26
	GMAW (Spray)	Room		136	90	15
		500	260	121	64	23
		1000	538	113	50	32
	SMAW	Room		130	87	13
		1000	538	109	48	32

* ksi can be converted to MPa (megapascals) by multiplying by 6.895.

Typical Tensile Data, All-Weld Metal

Weld Type	Test Temperature		Ultimate Tensile Strength, ksi*	Yield Strength at 0.2% Offset, ksi*	Elongation in 2 in. (50.8 mm), %
	°F	°C			
GTAW	Room	-	133	95	10
GMAW (Short)	Room	-	132	89	17
GMAW (Spray)	Room	-	123	85	18
SMAW	Room	-	134	93	16
	1000	-	100	61	31

* ksi can be converted to MPa (megapascals) by multiplying by 6.895.

Typical Impact Strength, Weldments

Weld Type	V-Notch Impact Strength Room Temperature	
	ft.-lb.	Joules
GTAW	94	127
SMAW	42	57

Typical Bend Test Data, Welded Plate

Weld Type	Face Bend		Side Bend	
	2T	3T	2T	3T
GMAW (Short)	Failed	Passed	Failed	Passed
GMAW (Spray)	Failed	Passed	Failed	Passed
SMAW	-	Passed	-	-

Duplicate specimens, 3/4 in. (19.10 mm) thick. Tested using AWS Specification 5.11 as a guide.

HEALTH AND SAFETY

Welding can be a safe occupation. Those in the welding industry, however, should be aware of the potential hazards associated with welding fumes, gases, radiation, electric shock, heat, eye injuries, burns, etc. Also, local, municipal, state, and federal regulations (such as those issued by OSHA) relative to welding and cutting processes should be considered.

Nickel-, cobalt-, and iron-base alloy products may contain, in varying concentration, the following elemental constituents: aluminum, cobalt, chromium, copper, iron, manganese, molybdenum, nickel and

tungsten. For specific concentrations of these and other elements present, refer to the Material Safety Data Sheets (MSDS) available from Haynes International, Inc.

Inhalation of metal dust or fumes generated from welding, cutting, grinding, melting, or dross handling of these alloys may cause adverse health effects such as reduced lung function, nasal and mucous membrane irritation. Exposure to dust or fumes which may be generated in working with these alloys may also cause eye irritation, skin rash and effects on other organ systems.

The operation and maintenance of welding and cutting equipment should conform to the provision of American National Standard ANSI/AWS Z49.1, "Safety in Welding and Cutting". Attention is especially called to Section 4 (Protection of Personnel) and 5 (Health Protection and Ventilation) of ANSI/AWS Z49.1. Mechanical ventilation is advisable and, under certain conditions such as a very confined space, is necessary during welding or cutting operations, or both, to prevent possible exposure to hazardous fumes, gases, or dust that may occur.

WELD OVERLAY

ULTIMET alloy is an ideal weld overlay material. Not only does it provide corrosion and wear protection to critical surfaces, it is very easy to apply compared with the traditional cobalt-base hardfacing alloys. This ease of application stems from its relatively high ductility. ULTIMET alloy may be applied in multiple layers with little or no preheat. Deposit cracking does not occur under most circumstances.

Weld overlays of ULTIMET alloy have been applied by gas

tungsten arc, gas metal arc, shielded metal arc, submerged arc and plasma transferred arc welding techniques.

Oxyacetylene process is not recommended. For submerged arc welding, Lincoln Blue-Max 2000 flux is recommended.


Postweld Heat Treatment

Under most conditions, the postweld heat treatment of ULTIMET weld deposits is not required. If bending or cold-forming of the deposits is necessary, an annealing

treatment at 2050°F (1121°C), followed by water quenching, may be required depending on the bend radius. The effects of annealing on the substrate material should be considered.

Stress-relief heat treatments in the temperature range of 1100 to 1200°F (593 to 649°C) do not markedly affect the properties of ULTIMET weld overlays. For further information, please consult Haynes publication H-2089 and H-2099.


Cruciform Test For Weld Cracking Sensitivity (Coated Electrodes)

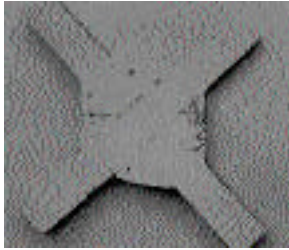

STELLITE 1
Hot cracked at 1st layer
(stopped after 16 beads)



STELLITE 6
Hot cracked at 3rd layer
(stopped after 24 beads)

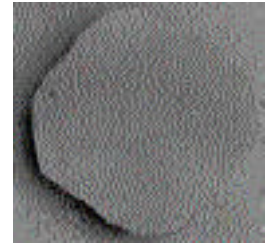

ULTIMET® alloy
No observed cracking
(Total of 160 beads)

MACHINING

ULTIMET alloy can be successfully turned, drilled, and milled provided appropriate tooling and parameters are employed. The alloy possesses high strength, and therefore resists metal removal. It also work hardens rapidly.

The alloy is most easily machined in the solution annealed condition. The following are guidelines for performing typical machining operations upon ULTIMET alloy wrought stock. Exact details for specific machining jobs will vary with circumstances of the

particular job. Other tool materials not listed here may be suitable for machining ULTIMET alloy under various conditions. For further information, please consult Haynes publication H-2086.

Recommended Tool Types and Machining Conditions

Operations	Carbide Tools
Drilling	Carbide-tipped drills are recommended. Use 135° included angle on point. Speed: 30-35 sfm. Feed: 0.002 in. rev. \leq 1/4 in. dia., 0.004 in. rev. $>$ 1/4 in. dia. Oil ¹ or water-base ² coolant. Coolant-feed carbide tipped drills may be economical in some setups.
Roughing; Turning or Facing	C-2 or C-4 grade: Positive rake square insert, 15° or 45° SCEA ³ , 1/32 in. nose radius. Tool holder: 5° pos. back rake, 5° pos. side rake. Speed: 90-100 sfm depending on rigidity of set up, 0.010 in. feed, 0.050-0.100 in. depth of cut Dry ⁴ , oil, or water-base coolant.
Finishing; Turning or Facing	C-2 or C-4 grade; Positive rake square insert, if possible, 15° or 45° SCEA, 1/32 in. nose radius. Tool holder: 5° pos. back rake, 5° pos. side rake. Speed: 110-115 sfm, 0.010-0.015 in. feed, 0.010-0.015 in. depth of cut. Dry or water-base coolant.
Milling:	C-2 grade Speed: 25-30 sfm Feed: 0.02 in. tooth \leq 3/4 in. dia., 0.003 in. tooth $>$ 3/4 in. dia. Oil or water-base coolant

- NOTES:**
- 1 Oil coolant should be a premium quality, sulfochlorinated oil with extreme pressure additives. A viscosity at 100°F from 50 to 125 SSU.
 - 2 Water-base coolant should be premium quality, sulfochlorinated water soluble oil or chemical emulsion with extreme pressure additives. Dilute with water to make 15:1 mix. Water-base coolant may cause chipping and rapid failure of carbide tools in interrupted cuts.
 - 3 SCEA - Side cutting edge angle or lead angle of the tool.
 - 4 At any point where dry cutting is recommended, an air jet directed on the tool may provide substantial tool life increase. A water-base coolant mist may also be effective.

Acknowledgments:

CARPENTER and 20CB-3 are registered trademarks of Carpenter Technology Corporation
 NITRONIC is a registered trademark of Armco Steel Corporation
 800HT is a registered trademark of Inco Family of Companies
 STELLITE is a registered trademark of Thermadyne Deloro Stellite Inc.

AVAILABILITY

For More Technical Detail Request the Following Haynes International Brochures:


H-2087	Reference Guide for Optimum Protection Against Corrosion and Wear
H-2099	Guidelines for Weld Surfacing with ULTIMET Wire
H-2089	ULTIMET alloy Welding Guidelines
H-2086	ULTIMET alloy Machining Guidelines
H-1034	Applicable Specifications

ULTIMET alloy Specifications

UNS	R31233
ASTM	B-815 (Rod)
ASTM	B-818 (Plate, Sheet, Strip)
ASME	Section VIII, Div. 1, Code Case 2121
DIN	CoCr26Ni9Mo5W No. 2.4681
NACE	MR-01-75 Section 4.1.6.3

Available Wrought Product Forms

Bar	(≥ 12.7 mm/0.5 in.)
Billet	Standard Sizes
Plate	Standard Sizes
Sheet	(≥ 1.6 mm/0.063 in.)
Wire	Standard Sizes
Weld Products	(GTA, GMA, SMA, SAW)

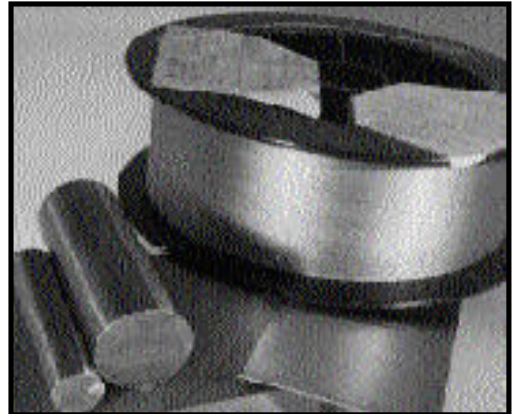

Castings

AOD Refined Master Alloy
(Remelt Bar) from
Cannon-Muskegon
Tel: 616-755-1681
Fax: 616-755-4016

Powders

Gas Atomized Powders For:
Plasma Transferred Arc (PTA) welding and
Thermal Spray Coating from
Deloro Stellite
Tel: 800-235-9353 or 574-534-2585
Fax: 574-534-3417

STANDARD PRODUCTS

By Brand or Alloy Designation:

HAYNES

International

HASTELLOY® Family of Corrosion-Resistant Alloys

B-3®, C-4, C-22®, C-276, C-2000®, C-22HS®, G-30®, G-35®, G-50®, HYBRID-BC1™, and N

HASTELLOY Family of Heat-Resistant Alloys

S, W, and X

HAYNES® Family of Heat-Resistant Alloys

25, R-41, 75, HR-120®, HR-160®, 188, 214®, 230®, 230-W®, 242®, 263, 282®, 556®, 617, 625, 65SQ®, 718, X-750, MULTIMET®, NS-163™, and Waspaloy

Corrosion-Wear Resistant Alloy

ULTIMET®

Wear-Resistant Alloy

6B

HAYNES Titanium Alloy Tubular

Ti-3Al-2.5V

Standard Forms: Bar, Billet, Plate, Sheet, Strip, Coils, Seamless or Welded Pipe & Tubing, Pipe Fittings, Flanges, Fittings, Welding Wire, and Coated Electrodes

Properties Data: The data and information in this publication are based on work conducted principally by Haynes International, Inc. and occasionally supplemented by information from the open literature, and are believed to be reliable. However, Haynes does not make any warranty or assume any legal liability or responsibility for its accuracy, completeness, or usefulness, nor does Haynes represent that its use would not infringe upon private rights.

Any suggestions as to uses and applications for specific alloys are opinions only and Haynes International, Inc. makes no warranty of results to be obtained in any particular situation. For specific concentrations of elements present in a particular product and a discussion of the potential health affects thereof, refer to the Material Safety Data Sheet supplied by Haynes International, Inc. All trademarks are owned by Haynes International, Inc.

Global Headquarters

1020 West Park Avenue

P.O. Box 9013

Kokomo, Indiana 46904-9013 (USA)

Phone: 1-800-354-0806 or (765) 456-6012

Fax: (765) 456-6905

www.haynesintl.com